



Surface anisotropy of iron oxide nanoparticles and slabs from first principles: Influence of coatings and ligands as a test of the Heisenberg model

Katarzyna Brymora, Florent Calvayrac

► To cite this version:

Katarzyna Brymora, Florent Calvayrac. Surface anisotropy of iron oxide nanoparticles and slabs from first principles: Influence of coatings and ligands as a test of the Heisenberg model. Journal of Magnetism and Magnetic Materials, 2017, 434, pp.14 - 22. 10.1016/j.jmmm.2017.03.034 . hal-01906076

HAL Id: hal-01906076

<https://univ-lemans.hal.science/hal-01906076>

Submitted on 17 Dec 2018

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Surface anisotropy of iron oxide nanoparticles and slabs from first principles : influence of coatings and ligands as a test of the Heisenberg model

Katarzyna Brymora, Florent Calvayrac

Institut des Molécules et Matériaux du Mans, PSC IMMM, CNRS UMR 6283, Université Bretagne Loire Université du Maine, Av. Messiaen, 72085 Le Mans Cedex 9, France

Abstract

We perform *ab initio* computations of the magnetic properties of simple iron oxide clusters and slabs. We consider an iron oxide cluster functionalized by a molecule or glued to a gold cluster of the same size. We also consider a magnetite slab coated by cobalt oxide. The changes in magnetic behavior are explored using constrained magnetic calculations. A possible value for the surface anisotropy is estimated from the fit of a classical Heisenberg model on *ab initio* results. The value found is compatible with estimations obtained by other means, or inferred from experimental results. The addition of a ligand, coating, or of a metallic nanoparticle to the systems degrades the quality of the description by the Heisenberg Hamiltonian.

Keywords:

surface anisotropy, magnetic nanoparticles, Heisenberg model, *ab initio*, functionalization

1. Introduction

Numerous experimental and theoretical studies have been performed in the last decade to provide an understanding of the properties of magnetic nanoparticles, such as super-paramagnetism or surface-enhanced anisotropy[1][2].

It has been proven possible to create nanoparticles built with alternating layers of various materials exhibiting different magnetic behaviors, which will

Email address: Florent.Calvayrac@univ-lemans.fr (Florent Calvayrac)

influence the magnetic moment structure at the surface or interface [3]. An induced magnetic anisotropy (exchange bias) can appear in such systems, corresponding to a shifted hysteresis loop and a ferrimagnetic alignment of the moments near the center of the nanoparticle as well as a pinning of the magnetic moments on the surface.

It has been demonstrated that surface modification by organic ligands have a strong influence on the magnetic structure of the nanoparticles (as described in the pioneering work of [4]) and also cause spin pinning near the surface [5].

Surface effects alone can change the magnetic structure, as it was demonstrated for instance in the case of cobalt [6], cobalt oxide [7], magnetite powders [8], and maghemite nanoparticles [9]. Those effects have been reviewed in the case of iron oxide in [10].

From the theoretical point of view, those effects and the related phenomena have been considered mainly from the phenomenological side. Typically, Monte-Carlo calculations on the classical Heisenberg model were performed [11], and results were compared to experimental data obtained on CO-functionalized NiPt clusters, as well as to DFT calculations where magnetic moments were computed in the collinear local density functional approach.

The Monte-Carlo-Metropolis approach was also used in the case of magnetite nanoparticles in [12]. In this work, the authors have demonstrated that the surface anisotropy constant can heavily influence the exchange-bias behavior. But this value remains a parameter and cannot even be precisely inferred from experimental data; only a range of possible values is estimated from the resulting magnetic behavior and the comparison to experiment.

The problem of the *ab initio* computing of the magnetic anisotropy at the surface of a nanoparticle will be the focus of this paper. In literature, this parameter is a phenomenological input in large scale classical calculations based on modified Heisenberg models. On the example of a small cluster, namely Fe_{13}O_8 we link various magnetically constrained calculations to a Heisenberg model in order to estimate magnetic properties of the nanoparticle from first principles. We study the change in magnetic properties due the presence of a ligand (dopamine) or of a nearby gold cluster. We also consider a magnetite surface, with an eventual cobalt oxide layer. We discuss the resulting pertinence of the description by a Heisenberg Hamiltonian.

2. Theory/calculation

2.1. Structure of the Chosen Systems

The first objective was to obtain an optimized structure of Fe_{13}O_8 , which according to mass spectrometry shows a higher abundance than other iron oxide clusters with different compositions [13]. We chose this system because it is small enough to be easily modelled by repetitive first-principle calculations and yet provide interesting surface effects, and was already structurally studied[17]. We used an *ab initio* ultrasoft pseudopotential scheme with a plane-wave basis as implemented in the Quantum Espresso (QE) suite ([14]). The plane wave basis set was defined by an energy cutoff of 30 Ry (408 eV), confirmed to be sufficient by the test of convergence. A mixing factor of 0.17 was employed. Integration in the first Brillouin zone was performed using 1x1x1 points sampling, since the system is an isolated cluster in a large computational cubic box of the size of 30 Å. The GGA density functional from PBE[15] was used with the corresponding pseudopotentials computed by A.dal Corso with the "rrkj3" code[16] and taken from the Quantum ESPRESSO pseudopotential data base. The optimization procedure was conducted without any symmetry. The structural results are close to the one previously reported in the literature[17].

We also considered two cases of infinite surfaces: first, a 001 oriented slab of magnetite with atomic positions taken from [18]. This system provides an interesting approach to magnetic nanoparticles of medical interest. The small surface to volume ratio of those nanoparticles of a diameter close to 10 nm makes possible the study of the grafting of ligands by considering a locally flat surface in order to reduce computational cost [?]. Another interest of such surfaces lies in their catalytic properties [?].

In a second step, we coated this surface in a close to epitaxial condition with 5 crystallographic units of a 012 surface of cobalt oxide, using periodic boundary conditions, and a vacuum of 12 atomic units on top, generated thanks to the ASE package [19], with the same computational conditions as previously described for the isolated cluster. The atomic positions, represented on figure 3, changed by less than 2 % in comparison to the input values after optimization, and the cell parameters changed by less than 1 %. A potential application of such a system might be found in the pinning of magnetic moments, and hence a change in hysteresis curves, from the coupling to antiferromagnetic materials [? ?]

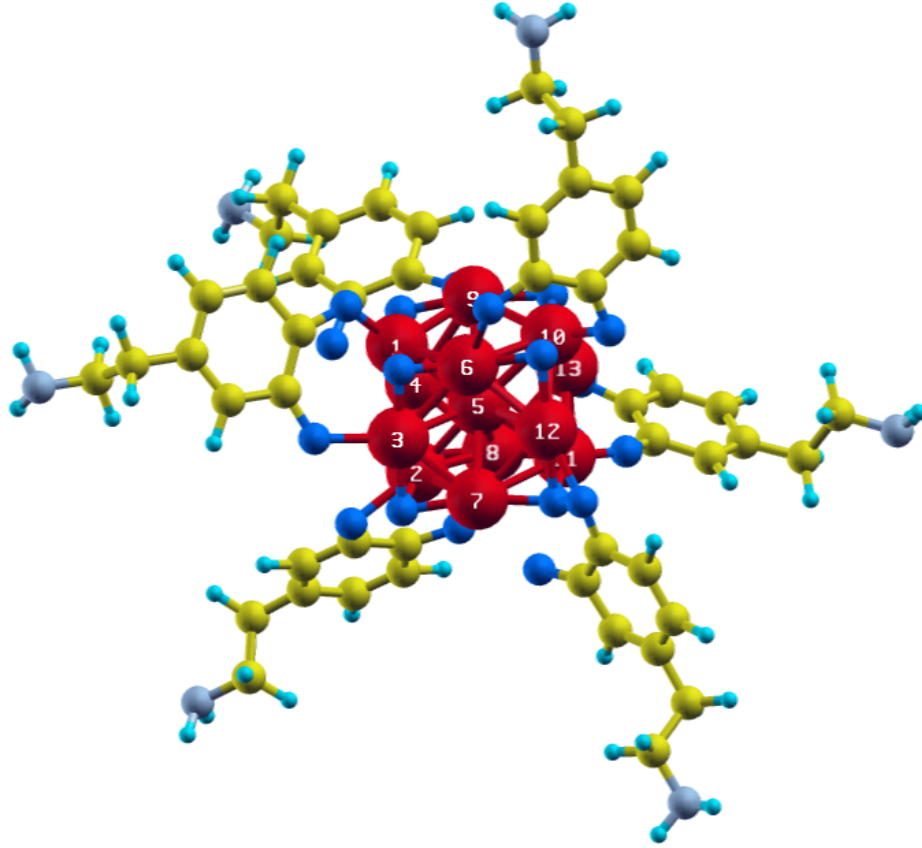


Figure 1: Fe_{13}O_8 cluster with six dopamine molecules.

From discussions with experimental teams [?] developing ferrites made of hybrid oxide nanoparticles we then tried a combined approach, generating a simple molecular dynamics simulation of a maghemite cluster coated with cobalt oxide, at 1000K, based on simple, Buckingham-like ionic potentials [24] and extracting several representative clusters of increasing size around a random atom. The atomic positions in these clusters were then optimized using the BFGS procedure within the Quantum Espresso suite with the same conditions discussed above, using periodic boundary conditions with a cubic cell of 32 atomic units. With the largest clusters discussed the systems are close to the bulk. We think that these clusters, even though the crystallography or the stoichiometry deviate from pure allotropic forms, reflect what can be found in a typical molecular dynamics run. One should note however that

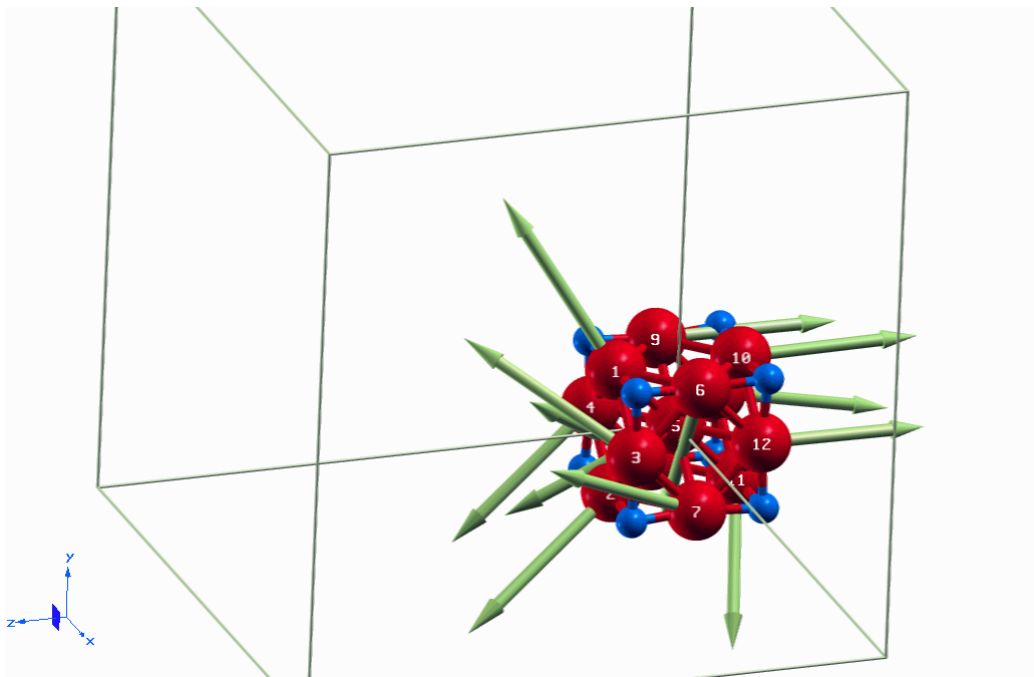


Figure 2: Result of a typical non-collinear constrained calculation of the iron oxide cluster ; here we imposed magnetic moments of 5,1 and 45 μ_B on each axis.

before optimization of the atomic positions, the magnetic moments around each iron or cobalt atom were found close to zero. A typical cluster is given on figure ??.

2.2. *Ab initio Magnetic Computation*

The change in local magnetic moments has been computed using the Quantum Espresso (PWSCF) code. We would like to note that such magnetic moments are sometimes referred to in the literature as "spins", when they are actually expectations on the values of spin components integrated over a sphere of reasonable but arbitrary radius centered on each atom. For the purpose of this calculations, we used non-collinear density functional theory[20].

We first considered four cases, Fe_{13}O_8 alone, with one dopamine molecule added, with six dopamine molecules (Fig. 1), and with a structurally optimized 20 atoms gold cluster in the framework of non-collinear magnetism calculations. We then considered a magnetite surface coated or not by cobalt

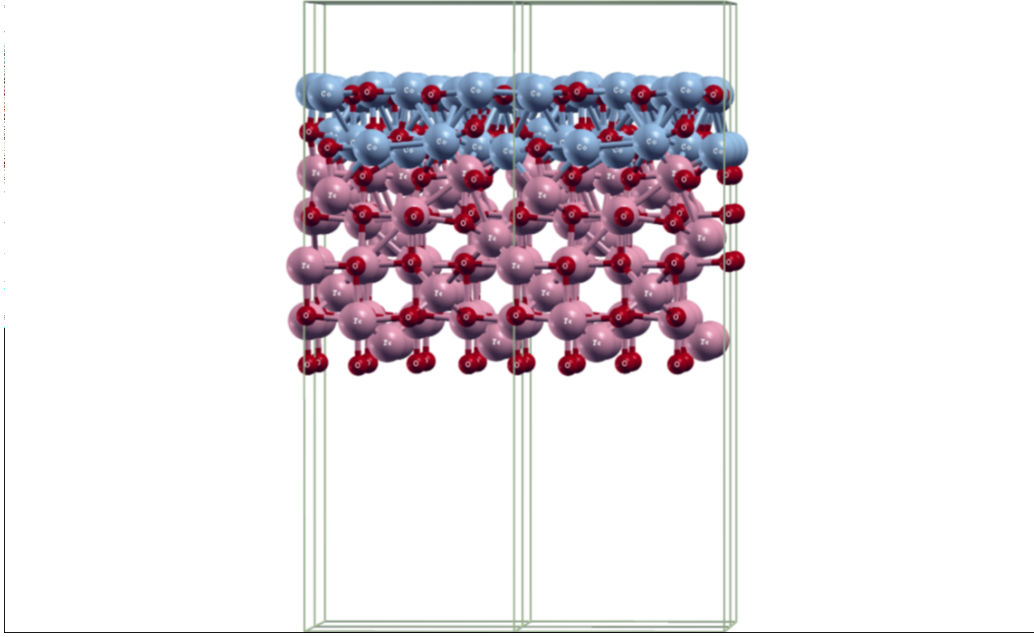


Figure 3: Atomic positions in a magnetite slab coated with cobalt oxide

oxide. In the case of magnetic computations we found that a reduction of the cutoff energy by half ensured consistency of the results (a convergence test showed that a cutoff energy of 30 Ry is a sufficient value to compute structural properties), and a 0.17 mixing factor for self-consistency was employed. A smearing factor of 0.02 Ry was used. We performed calculations assuming the systems to be isolated (in the case of the cluster) with a Martyna-Tuckerman correction [21]. We checked the results by performing calculations with relativistic pseudopotentials and spin-orbit coupling which we generated from the values suggested in the QE distribution for cutoff (1.4 and 1.6 a.u for Oxygen with 6 active electrons and a projector on empty $3d$ states), and the ultrasoft pseudopotentials without spin-orbit as described previously.

We enforced a set of arbitrary magnetization states different from the ground-state result but close to it within $2 \mu_b$ in each direction, and extracted the corresponding magnetic field from the converged values, using the constrained magnetic calculation option from the latest version of the Quantum Espresso code, which gives the magnetic field as a function of the distribution of magnetic moments. We used a penalty factor of 0.001 for this purpose in order to speed up convergence under this external constraint.

In the case of the isolated clusters, we found a magnetic structure rather hard to describe in simple terms. In the case of the magnetite surface, we found, as known from the literature, a slightly ferrimagnetic state with a resulting magnetization of zero along the x and y axes and of $0.17 \mu_B$ in the z direction, orthogonal to the surface, with an absolute magnetization of $2.48 \mu_B$. In the case of the magnetite surface coated by cobalt oxide, we found an enhancement of total magnetization, to $9.89 \mu_B$ in the z direction, as expected experimentally.

2.3. Magnetic Model

The previous procedure gives a distribution of local magnetic moments (\vec{S}_i), magnetic fields (\vec{H}), and total energies (H). We have collected these values from various QE runs under different constraints, varying the total magnetization in either direction by a few μ_B , and fitted the parameters from the Heisenberg Hamiltonian[12], given as:

$$\begin{aligned}
H = & - 2 \sum_{\langle i,j \rangle} J_{\langle i,j \rangle} \vec{S}_i \cdot \vec{S}_j \\
& - K_V \sum_i \left(S_{x,i}^2 S_{y,i}^2 + S_{y,i}^2 S_{z,i}^2 + S_{x,i}^2 S_{z,i}^2 \right) \\
& - K_S \sum_k \left(\vec{S}_k \cdot \vec{e}_k \right)^2 - g \mu_B \vec{H} \cdot \sum_i \vec{S}_i
\end{aligned} \tag{1}$$

It is to be noted here that the Zeeman energy (last term) is absent from QE results.

The first sum involves nearest neighbors interactions between iron atoms. In reference[12] these were computed as from coordination numbers. In the bulk three different coordination numbers appear: $z_{AA} = 4$, $z_{BB} = z_{BA} = 6$, and $z_{AB} = 12$. These numbers apply for the core of the nanoparticle. In our case, these numbers were computed from the coordinates of the iron atoms, enforcing a cutoff radius such that no atom had more than 12 neighbors.

The second term in the Hamiltonian is the core cubic magneto- crystalline anisotropy and reference[12] chose a value of $K_V = 0.002 \text{ meV / spin}$

The third term accounts for the single-ion site surface anisotropy where the unitary vector reads

$$\vec{e}_k = \frac{\sum_j \vec{P}_k - \vec{P}_j}{|\sum_j \vec{P}_k - \vec{P}_j|} \quad (2)$$

with \vec{P}_i the position vector of each iron atom on the surface and the sum runs over iron neighbors of j .

In reference[12] the exchange parameters were set at a value of $J_{AA} = -0.11$ meV, $J_{BB} = +0.63$ meV, and $J_{AB} = -2.92$ meV corresponding to a mix of ferromagnetic and anti-ferromagnetic interactions. Those values were taken from[22] where they were fitted on *ab initio* results using a method similar in principle to the one with presently discussed : bulk spin waves were fitted to non-collinear spin calculations.

2.4. Fitting Procedure

The results of the *ab initio* calculations (energies) were fitted using the Monte-Carlo Metropolis result method, based on random configurations of the parameters.

We used a basic, proven quasi-random recurrence generator [23] and a Metropolis algorithm where we accept configuration changes (in our case, a change of the Heisenberg parameters) ($q'_i = q_i + \Delta q_i$) corresponding to a $\Delta E = E'(q'_i) - E(q_i)$ change in the virtual energy of the system. The virtual energy E is here a penalty function representing the distance in between the set of energies found with *ab initio* calculations and these found with the Heisenberg model applied to the distribution of moments. The change is accepted if a random number y uniformly drawn in between 0 and 1 is lower than $P(\Delta E, T)$.

To fit the *ab initio* results using the Metropolis simulated annealing method we choose the following parameters: a reference energy H_0 (fit parameter), the set of $J_{<i,j>}$ (enforcing $J_{<i,j>} = J_{<j,i>}$), K_V , K_S and g . We first used a small set of $J_{<i,j>}$ corresponding to a small cutoff in neighborhood search, then increased the number of neighbors to increase the quality of the fit. In order for the results to keep a physical meaning we kept the total number of fitted parameters (maximum of 40) well under the number N of samples used to define the virtual energy or penalty function from the energies in Rydbergs:

$$E = \frac{1}{N} \sum_i^N |H_{\text{ab initio}} - H_{\text{Heisenberg}}|$$

In the case of the isolated cluster, since the set of $J_{\langle i,j \rangle}$ is not too large, we allowed those to take any value, but in the case of the surfaces, the large number of $J_{\langle i,j \rangle}$ gave an excellent fit anytime, whatever the conditions, and the distribution of values obtained was hard to read. Therefore, in this latter case, we used the same model already used in [24], namely two parameters for each kind of super-exchange(iron-iron, iron-cobalt or cobalt-cobalt) related to the super-exchange angle θ in between atoms separated by an oxygen atom, using the relation

$$J_\theta = J_{180^\circ} \cos^2 \theta + J_{90^\circ} \sin^2 \theta \quad (3)$$

which can be written in the form

$$J_\theta = J_{90^\circ} + (J_{180^\circ} - J_{90^\circ}) \cos^2 \theta \quad (4)$$

where J_{90° and J_{180° are the coupling constant corresponding to the super-exchange angle of 90° and 180° , respectively. Those two parameters per couple of atoms (therefore six in total) are the only ones fitted in the model with the volume and surface anisotropies.

In the case of the isolated cluster we also modified the Heisenberg Hamiltonian in the model to allow for a local change in surface anisotropy ending up with:

$$\begin{aligned} H = & H_0 - 2 \sum_{\langle i,j \rangle} \vec{J}_{\langle i,j \rangle} \vec{S}_i \cdot \vec{S}_j \\ & - K_V \sum_i (S_{x,i}^2 S_{y,i}^2 + S_{y,i}^2 S_{z,i}^2 + S_{x,i}^2 S_{z,i}^2) \\ & - \sum_k K_{Sk} (\vec{S}_k \cdot \vec{e}_k)^2 - g\mu_B \vec{H} \cdot \sum_i \vec{S}_i \end{aligned} \quad (5)$$

We also had to chose several parameters of the simulated annealing procedure such as the fictitious temperature, the annealing law, and the dependence of random changes to the temperature.

All the software used is archived on

http://perso.univ-lemans.fr/~fcalvay/surf_anis_code

3. Results and Discussion

3.1. Iron Oxide Clusters

We generated sets of $N = 101$ configurations randomly drawn from *ab initio* results corresponding to a total enforced magnetization running from l to $5 \mu_B$ along the x axis, 1 to 5 along the y axis, and 37 to 41 μ_B along the z axis.

The best result (penalty function as defined above less than 10^{-4}Ry) was, as could be expected from the increased number of degrees of freedom in the model, found using the largest number of fitting parameters (full set of $J_{<i,j>}$ and set of surface anisotropy constants K_{Sk}). A typical fit of *ab initio* values versus Heisenberg model is given in Fig. 4; in this case it can be seen that the Heisenberg model seems to model correctly the *ab initio* results. A further confirmation is found in the fact that the g factor is obtained with a value lower than 10^{-2} confirming that the absence of Zeeman energy in the QE code results is found by the fitting procedure.

A histogram of the obtained parameters for the $J_{<i,j>}$ is illustrated in Fig. 6. It can be seen that those values are close to the ones of reference[22], with an alternation of ferromagnetic and anti-ferromagnetic couplings.

The volume anisotropy was found to have a value of -2×10^{-05} a.u, coherent with the one used in[12]. The values for the local surface anisotropy constants are given in Table 1. It can be seen that the best fit corresponds to an alternation of positive and negative values for those constants. This fact raises the question of the validity of the Hamiltonian used in[12] in which a constant surface anisotropy was used.

Indeed, we found that the model does not adjust as well when we use a constant surface anisotropy. The best penalty was found at a value of 1.13×10^{-3} Ry. This corresponds to a value of the surface anisotropy of 1.753 a.u and a volume anisotropy of 6.31×10^{-05} a.u. The latter value is now positive, but the authors of[12] found that the K_S/K_V ratio is the more important parameter to predict the magnetic structure of a nanoparticle of intermediate size. Here, the value of 27780 we find for this ratio hints at a hedgehog type magnetic structure (Fig. 2). It might be that the large surface contribution of such a small system as the one we study is responsible for this fact, but at least the value we find is not a free, almost unknown parameter as in the literature. Physically, such a result would correspond to jumps during magnetization reversal, and exchange bias properties. Such results have been experimentally observed and are also reviewed in[12].

Fe atom	Surface anisotropy in a.u.
1	$0.5592594 \times 10^{-01}$
2	$-0.5450376 \times 10^{-01}$
3	$0.4755301 \times 10^{-01}$
4	$-0.2952414 \times 10^{-01}$
5	$0.4511738 \times 10^{-01}$
6	$0.5525300 \times 10^{-01}$
7	$-0.4852317 \times 10^{-01}$
8	$-0.2241407 \times 10^{-01}$
9	$0.8430323 \times 10^{-01}$
10	$-0.7067873 \times 10^{-02}$
11	$-0.7141519 \times 10^{-01}$
12	$-0.7437612 \times 10^{-01}$
13	$-0.8089262 \times 10^{-01}$

Table 1: Local surface anisotropy constants

When we tried the same method with full spin-orbit coupling and relativistic pseudopotentials, the increased disorder in the magnetic moments resulted in a penalty function of 2×10^{-3} Ry, with essentially similar results for the fitting parameters.

3.2. Iron Oxide Clusters and Dopamine

Linking to previous work [?] on the coating of magnetic nanoparticles by various ligands in order to make them more biocompatible or to link to antibodies in order to better target tumors, we then added a dopamine molecule next to the cluster from the previous section and, after optimizing the atomic positions, tried the same fitting procedure with a Heisenberg model. It turned out that we could not achieve a fit with a penalty function better than 5×10^{-3} Ry, which more or less corresponds to the distribution of energies in the *ab initio* results, and unrealistic coupling constants as well as a strongly unstable distribution of surface anisotropy constants. We concluded that a Heisenberg model might be too simple to describe such a system, where electrons donated by the dopamine molecule can lead to some itinerant magnetism, or at least to some symmetry breaking. The accuracy of *ab initio* results could also maybe be improved to the expense of computational time, but since the fitting procedure works in isolated cases

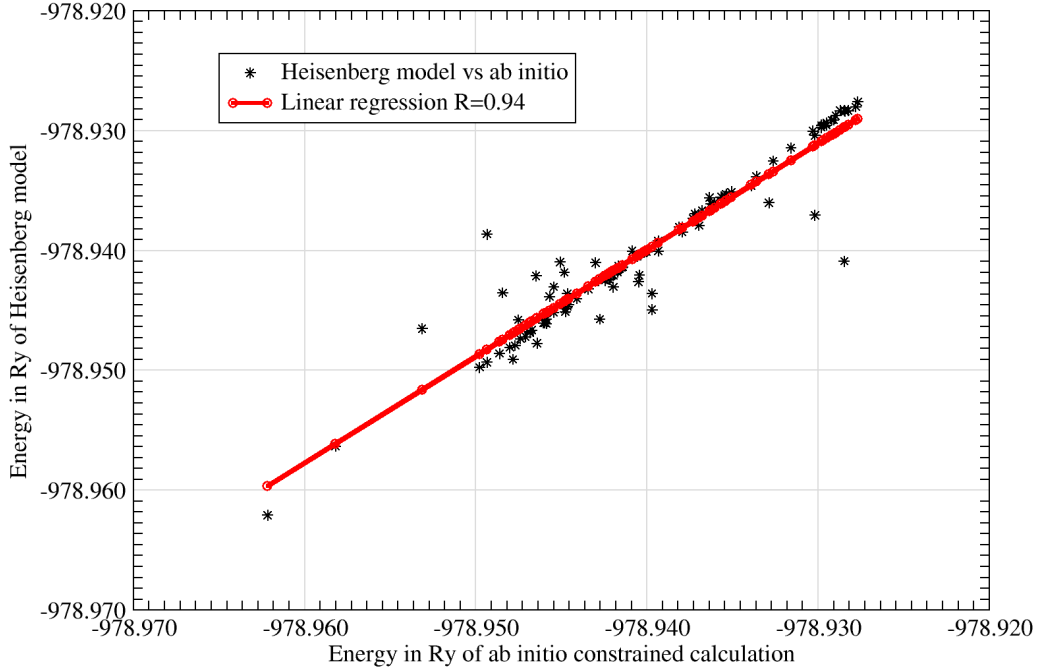


Figure 4: Results of the *ab initio* calculations fitted using the Monte-Carlo Metropolis (without spin-orbit) in the case of the isolated Fe_{13}O_8 cluster.

the origin of the lack of fit seems to come more from the model than from the quality of the results on which it is fitted.

In order to address the question of the symmetry breaking, we added 6 dopamine molecules (Fig. 1) symmetrically distributed around the cluster. The simulation time was found to be too large to compute as many constrained points as in the previous section, but, by plotting the magnetization as a function of the magnetic field, as can be seen in Fig. 7, we could check that the response of the system seems to be unchanged from this functionalization.

3.3. Iron Oxide Clusters and Gold Cluster

We also tried to introduce in the system a small gold cluster (which could act as a nano-antenna in plasmonics) which was found after structural optimization to adhere to the iron oxide cluster. In this case, the Heisenberg model did not fit very well either the computed *ab initio* values of energies.

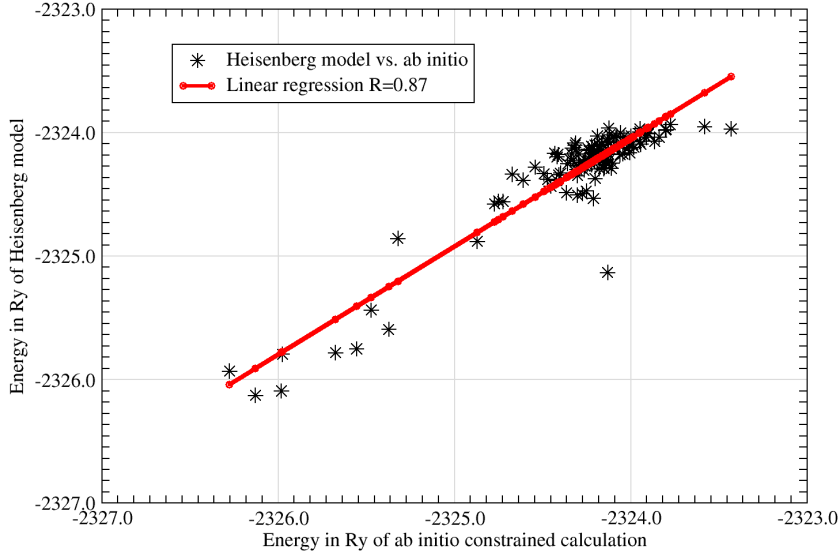


Figure 5: Results of the *ab initio* calculations fitted using the Monte-Carlo Metropolis in the case of the magnetite surface

However, as can be seen in Fig. 7, although the absolute values of external magnetic field to achieve the same total magnetization along the x axis are strongly different from the previous cases (with or without dopamine), the slope of the curve is similar.

3.4. Magnetite surface and magnetite coated with cobalt oxide

In the case of the magnetite surface, generating 124 samples for 6 parameters, we found the best fit, with a correlation coefficient of 0.87 in between the *ab initio* results and the fit for a surface anisotropy of 784.00 meV, a volume anisotropy of 6.96×10^{-3} meV, a Land g factor close to zero (which we see as a proof of correctness of our model), and coupling constants used to generate the $J_{<i,j>}$ of 1.102 meV and 2.076 meV respectively. The results of the fit are shown on figure 5 and, in this case also, we conclude that the Heisenberg model corrected with a surface anisotropy term gives a good description of the magnetism of the system. The values we find for volume

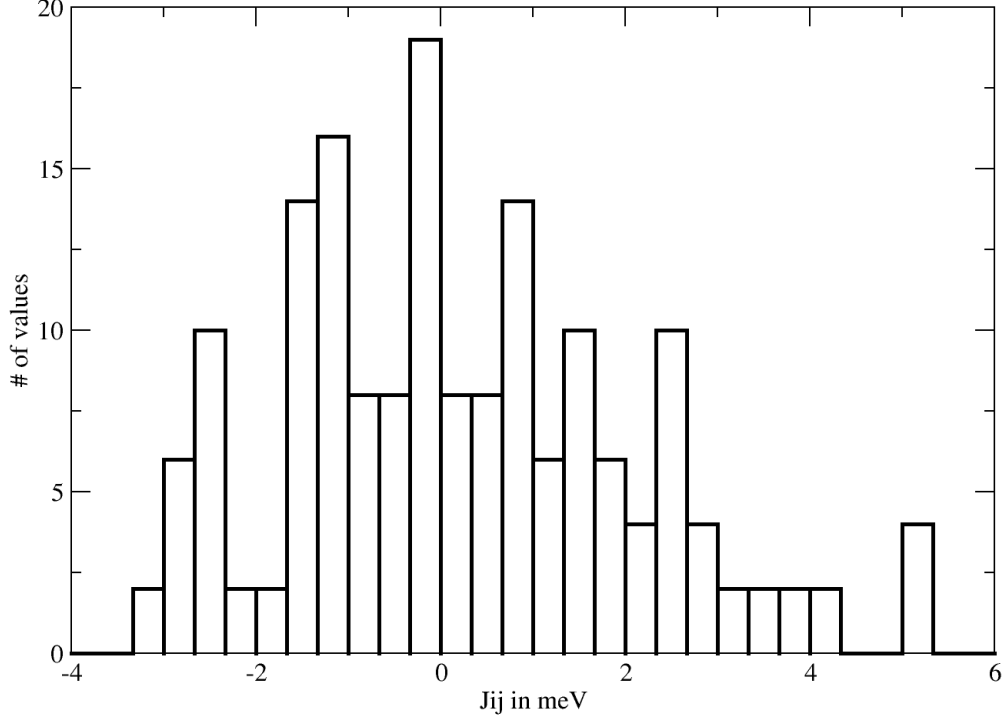


Figure 6: Histogram of exchange constants found by the fitting procedure on the iron oxide cluster.

anisotropy is in good agreement with the literature, and the ratio of surface to volume anisotropy is in the range expected by experimentalists.

In the case of the magnetite surface coated by iron oxide, in which we could only generate 55 samples due to the much higher numerical cost, we found that the model was much harder to fit (with a correlation coefficient of only .54 in between the ab initio values and the fitted values). The best fit was obtained with a surface anisotropy of 546.77 meV, volume anisotropy of 2.63×10^{-3} meV, and coupling constants of 0.98 meV and 2.11 meV in the case of iron-iron, 0.77 meV and 2.09 meV in the case of iron-cobalt, and 0.97 meV and 2.37 meV in the case of cobalt-cobalt pairs. In this case, either a better ab initio calculation would have been needed (using for instance the LDA+U method in order to better describe the insulating behavior of cobalt oxide), or the magnetic model has to be improved, including for instance

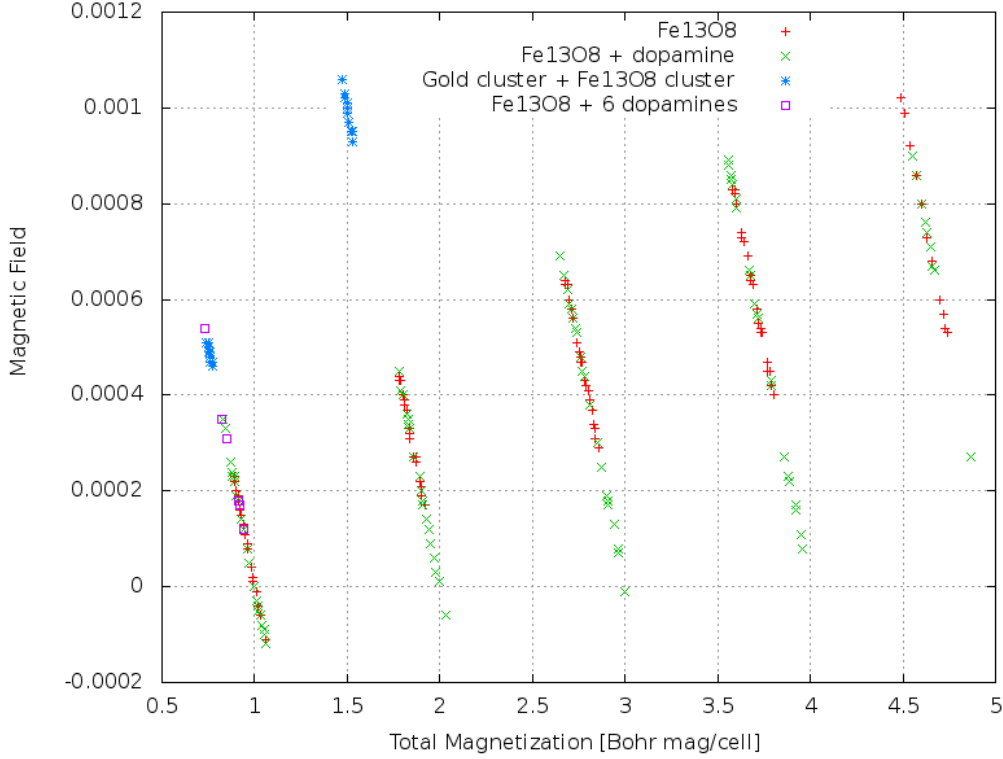


Figure 7: Magnetic moments vs. magnetic field extracted from the constrained calculation for the studied clusters

interface anisotropy terms.

3.5. Mixed iron oxide and cobalt oxide clusters

We then addressed the case of clusters of iron, cobalt and oxygen atoms of increasing size, which we submitted to a global magnetic constraint, namely a global angle of respectively 5,30,45 and 75 degrees with respect to the z axis, cases to which we will refer as numbers 0 to 3 later. This constraint allows to get a value of the magnetic field from the ab initio calculations.

In order to estimate the change in the anisotropy term from the cobalt/iron mixing, after various functional tries, we found that the best fit was obtained when we allowed a change in the volume and surface anisotropy term depending on the number of iron and cobalt atoms present in the cluster. The additional term was multiplied by adjustable parameters a_i (where i

represents iron and cobalt atoms), so if there are N different species in the system with n_i atoms of each kind per cell for the volume term or per surface site in the case of surfaces, the volume and surface anisotropies read

$$K_{S,V,i} = K_{S,V}^0 a_i^{n_i} \quad (6)$$

so that the final Hamiltonian we used reads

$$\begin{aligned} H = & - 2 \sum_{\langle i,j \rangle} J_{\langle i,j \rangle} \vec{S}_i \cdot \vec{S}_j \\ & - \sum_i K_{V,i} (S_{x,i}^2 S_{y,i}^2 + S_{y,i}^2 S_{z,i}^2 + S_{x,i}^2 S_{z,i}^2) \\ & - \sum_k K_{S,k} (\vec{S}_k \cdot \vec{e}_k)^2 - g\mu_B \vec{H} \cdot \sum_i \vec{S}_i \end{aligned} \quad (7)$$

The advantage of the modification of the volume and surface anisotropies we used in equation 6 is that such a term allows simply to take into account the changes in anisotropy due to a varying ratio of cobalt to iron atoms.

We tried to include a factor in the Hamiltonian in order to modelize the effect of the various oxygen stoichiometries of the clusters on the energy but for the functional form we tried (multiplying each anisotropy term by the ratio of magnetic to oxygen atoms) we found that the corresponding parameter was converging to zero.

The values of the parameters converged to values presented in table 2

As can be seen on figure 8 the fitting procedure of the Hamiltonian converged to a satisfying level, with a correlation coefficient close to 1 in between ab initio values of the magnetic energy and energies given by the model. We then dropped from the fitting procedure several configurations chosen at random, in order to check the predictive capabilities of the model (points labeled with an impulse), which can be seen as satisfying, despite obviously less good than the ones given by the model when reusing the input configurations used for fitting as in the previous case. The model can nevertheless be seen as adequate, since it uses only 12 fit parameters for 30 couples of input values, and has some predictive power.

From the physical results one can see that the values of the exchange constants kept the same order of magnitude as in the previous case of pure surfaces, although the values changed, with an interesting information for

Parameter	value
K_S^0	
749.15 meV	
K_V^0	
4.43 meV	
$a_{Fe,S}$	
2.20	
$a_{Fe,V}$	
1.66	
$a_{Co,S}$	
1.33	
$a_{Co,V}$	
0.48	
$J_{Fe,90^\circ}$	
0.77 meV	
$J_{Fe,180^\circ}$	
1.39 meV	
$J_{FeCo,90^\circ}$	
0.70 meV	
$J_{FeCo,180^\circ}$	
1.17 meV	
$J_{Co,90^\circ}$	
-1.25 meV	
$J_{Co,180^\circ}$	
-1.35 meV	

Table 2: Parameters obtained for mixed iron oxide / cobalt oxide clusters

Fe/Co pairs. The same goes for the surface and volume anisotropies, with an enhancement in the case of iron oxide in comparison to cobalt oxide, the mixed situations being intermediate. One should note that in the total energies, the main contribution comes from the surface term, followed respectively by the volume and exchange contributions. It is then no wonder that the latter term is particularly difficult to adjust.

A problem remaining to be solved is that for the time being, we do not have at our disposal a clear physical way to predict the magnetic moments

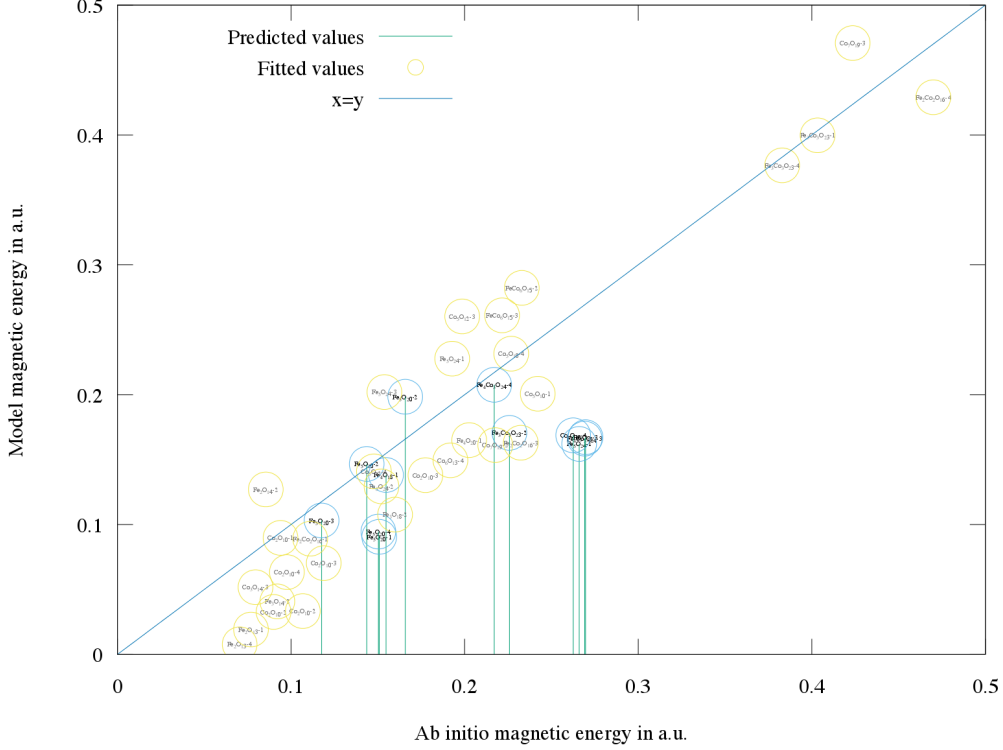


Figure 8: Results of fitting the Heisenberg model on mixed iron oxide and cobalt clusters under varying magnetic constraints

emerging from a given configuration of atoms. A machine learning approach based on physically relevant data such as relative angles and distances can be envisaged ; nevertheless the present study gives surface anisotropy values from an adjustment over *ab initio* results, and if values of magnetic moments are set to physically reasonable values as found in the bulk, can give a phenomenological description of magnetic nanoparticles of large size if the geometric configurations of atoms do not diverge too much from the bulk.

4. Conclusions

In this work, we adjusted a classical Heisenberg model of magnetism using the Metropolis simulated annealing method including surface anisotropy effects on magnetically constrained, non collinear *ab initio* results obtained a small iron oxide cluster functionalized or not by one or several dopamine

molecules or a nearby gold cluster. We conclude that the Heisenberg model seems to apply well to the simpler systems (namely, a free iron oxide cluster or a magnetite surface), allowing us to give some absolute values of the surface anisotropy constant, although a locally varying surface anisotropy alternating positive and negative values seem to provide a better description.

This could allow us to describe the magnetic behavior of a nanoparticle of size 1 to 10 nm, which *ab initio* calculations can hardly tackle for the time being because of computing power limitations, hoping that the large surface proportion of iron atoms in the small cluster we have studied does not influence the results.

In the case of functionalized cluster by one or several molecules of dopamine, or by a nearby gold cluster, the Heisenberg picture does not apply as well as for the simpler system, but we could nevertheless observe that the linear relation in between magnetic field and magnetization was unchanged in all those cases even if absolute values changed.

In the case of clusters of varying sizes and compositions, with periodic boundaries conditions, we were able to give a model describing hybrid ferromagnetic and antiferromagnetic systems, describing the enhancement in surface anisotropy due to the juxtaposition and mixing of the systems and giving estimations of the corresponding values.

Assuming fixed magnitudes for the magnetic moments of the atoms, the hamiltonian we present in the present publication can be used to describe the magnetic order in similar systems including transition metal atoms , as we checked on examples non included in the fitting procedure.

5. Acknowledgments

We thank S.Ammar and I.Labaye for fruitful discussions. K.B. was supported by a grant from the French Education and Research Minister. We thank GENCI/IDRIS and CRIHAN for computational time (projects x2014096171 and 007 respectively)

6. References

- [1] R. H. Kodama, Magnetic nanoparticles, Journal of Magnetism and Magnetic Materials 200 (13) (1999) 359 – 372.

- [2] A.-H. Lu, E. Salabas, F. Schüth, Magnetic nanoparticles: Synthesis, protection, functionalization, and application, *Angewandte Chemie International Edition* 46 (8) (2007) 1222–1244.
- [3] E. Tronc, D. Fiorani, M. Nogus, A. Testa, F. Lucari, F. Dorazio, J.-M. Grenèche, W. Wernsdorfer, N. Galvez, C. Chanac, D. Mailly, J. Jolivet, Surface effects in noninteracting and interacting gamma-Fe₂O₃ nanoparticles, *Journal of Magnetism and Magnetic Materials* 262 (1) (2003) 6 – 14.
- [4] A. E. Berkowitz, J. A. Lahut, I. S. Jacobs, L. M. Levinson, D. W. Forester, Spin Pinning at Ferrite-Organic Interfaces, *Phys. Rev. Lett.* 34 (10) (1975) 594–597.
- [5] Y. Kseolu, Effect of surfactant coating on magnetic properties of Fe₃O₄ nanoparticles: {ESR} study, *Journal of Magnetism and Magnetic Materials* 300 (1) (2006) e327 – e330.
- [6] F. Luis, J. Torres, L. Garcia, J. Bartolomé, J. Stankiewicz, F. Petroff, F. Fettar, J.-L. Maurice, A. Vauras, Enhancement of the magnetic anisotropy of nanometer-sized Co clusters: Influence of the surface and of interparticle interactions, *Physical Review B* 65 (9).
- [7] P. Hajra, P. Brahma, S. Dutta, S. Banerjee, D. Chakravorty, Enhancement of magnetic anisotropy in mechanically attrited Cr₂O₃ nanoparticles, *Journal of Magnetism and Magnetic Materials* 324 (7) (2012) 1425–1430.
- [8] A. Kihal, G. Fillion, B. Bouzabata, B. Barbara, High field surface magnetic study of Fe₃O₄ nanoparticles, *physica status solidi (b)* 249 (3) (2012) 604–614.
- [9] K. Nadeem, H. Krenn, T. Traussnig, R. Wurschum, D. V. Szaboi, I. Letofsky-Papst, Spin-glass freezing of maghemite nanoparticles prepared by microwave plasma synthesis, *Journal of Applied Physics* 111 (11) (2012) 113911.
- [10] E. Tronc, A. Ezzir, R. Cherkaoui, C. Chanac, M. Nogues, H. Kachkachi, D. Fiorani, A. M. Testa, J. M. Grenèche, J. P. Jolivet, Surface-related properties of -Fe₂O₃ nanoparticles, *Journal of Magnetism and Magnetic Materials* 221 (1) (2000) 63–79.

- [11] D. A. van Leeuwen, J. M. Van Ruitenbeek, L. J. De Jongh, A. Ceriotti, G. Pacchioni, O. D. Haberlen, N. Resch, Quenching of magnetic moments by ligand-metal interactions in nanosized magnetic metal clusters, *Phys. Rev. Lett.* 73 (10) (1994) 1432–1435.
- [12] J. Mazo-Zuluaga, J. Restrepo, F. Munoz, J. Mejia-Lopez, Surface anisotropy, hysteretic, and magnetic properties of magnetite nanoparticles: A simulation study, *Journal of Applied Physics* 105 (12) (2009) 123907.
- [13] Q. Sun, B. V., M. Marquez, P. Jena, C. Gonzalez, Q. Wang, Theoretical study on gold-coated iron oxide nanostructure: Magnetism and bioselectivity for amino acids, *The Journal of Physical Chemistry C* 111 (2007) 4159–4163.
- [14] P. Giannozzi, S. Baroni, N. Bonini, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, G. L. Chiarotti, M. Cococcioni, I. Dabo, A. Dal Corso, S. de Gironcoli, S. Fabris, G. Fratesi, R. Gebauer, U. Gerstmann, C. Gougoussis, A. Kokalj, M. Lazzeri, L. Martin-Samos, N. Marzari, F. Mauri, R. Mazzarello, S. Paolini, A. Pasquarello, L. Paulatto, C. Sbraccia, S. Scandolo, G. Sclauszero, A. P. Seitsonen, A. Smogunov, P. Umari, R. M. Wentzcovitch, Quantum espresso: a modular and open-source software project for quantum simulations of materials, *Journal of Physics: Condensed Matter* 21 (39) (2009) 395502.
- [15] J. P. Perdew, K. Burke, M. Ernzerhof, Generalized gradient approximation made simple, *Phys. Rev. Lett.* 77 (1996) 3865–3868.
- [16] A. D. Corso, A. M. Conte, Spin-orbit coupling with ultrasoft pseudopotentials: Application to au and pt, *Phys. Rev. B* 71 (2005) 115106.
- [17] Q. Wang, Q. Sun, M. Sakurai, J. Z. Yu, B. L. Gu, K. Sumiyama, Y. Kawazoe, Geometry and electronic structure of magic iron oxide clusters, *Phys. Rev. B* 59 (1999) 12672–12677.
- [18] S. Grazulis, A. Daskevicius, A. Merkys, D. Chateigner, L. Lutterotti, M. Quaresima, N. R. Serebryanaya, P. Moeck, R. T. Downs, A. Le Bail, Crystallography Open Database (COD): an open-access collection of crystal structures and platform for world-wide collaboration, *Nucleic acids research* 40 (D1) (2012) D420–D427.

- [19] S. R. Bahn, K. W. Jacobsen, An object-oriented scripting interface to a legacy electronic structure code, *Comput. Sci. Eng.* 4 (3) (2002) 56–66.
- [20] U. v. Barth, L. Hedin, A local exchange-correlation potential for the spin polarized case : I, *Solid State Phys* 5 (1972) 1629.
- [21] G. J. Martyna, M. E. Tuckerman, A reciprocal space based method for treating long range interactions in ab initio and force-field-based calculations in clusters, *The Journal of Chemical Physics* 110 (6) (1999) 2810–2821.
- [22] M. Uhl, B. Siberchicot, A first-principles study of exchange integrals in magnetite, *Journal of Physics: Condensed Matter* 7 (22) (1995) 4227.
- [23] W. H. Press, B. P. Flannery, S. A. Teukolsky, W. T. Vetterling, *Numerical Recipes in Fortran 77: The Art of Scientific Computing*, Cambridge University Press, NY, 1992.
- [24] B. Fongang, Y. Labaye, F. Calvayrac, S. Zekeng, J.-M. Grenèche, Coupled structural and magnetic properties of ferric fluoride nanostructures: Part II, a Monte Carlo-Heisenberg study, *Journal of Magnetism and Magnetic Materials* 324 (22) (2012) 3646–3651.